

N° d'enregistrement

au C.N.R.S.

432

ARTICLE PRINCIPAL

recouvrant en partie

LA THESE DE DOCTORAT ES-SCIENCES PHYSIQUES

présentée

A LA FACULTE DES SCIENCES DE PARIS

par

Jean-Claude PICARD

pour obtenir

Le Grade de Docteur ès-Sciences

Sujet de la thèse : Résonance cyclotron en ondes sub-millimétriques. Application à l'étude de la bande de valence du Tellure.

Soutenue le 18-2-67 devant la Commission d'Examen

MM. J. FRIEDEL : Président

J. BOK : Examineur

Ph. NOZIERES : Examineur

P. AIGRAIN : Invité

Cyclotron Resonance in Tellurium at Submillimeter Wavelengths[†]

J. C. PICARD* and D. L. CARTER

*Laboratoire de Physique de l'Ecole Normale Supérieure,
Paris, France*

Magneto transmission experiments in the Voigt configuration at wavelengths from 730 to 940 μ have been performed on Te single crystals with $2-3 \times 10^{13}$ carriers cm^{-3} and $\mu = 5 \times 10^4 \text{ cm}^2/\text{V sec}$ at 4.2°K, using carcinotron fundamental sources.

The observed cyclotron resonances were fit by a single mass ellipsoid of revolution about the *C* axis with $m_1 = m_2 = 0.109 m_0$, $m_3 = 0.264 m_0$. An anisotropy in the relaxation time was deduced from the curve shapes which agrees with earlier transport measurement.

§ 1. Introduction

We have developed an experimental method which allows us to observe cyclotron resonance at submillimeter wavelengths and liquid helium temperatures. Operating at wavelengths between the usual microwave spectrometers which currently work down to 2 mm and optical set-ups, it combines elements of both techniques and permits the observation of cyclotron resonance in samples of moderate mobility. At $\lambda = 4 \text{ mm}$ (70 Gc/s) for a carrier of effective mass $0.1 m_0$ the magnetic field at resonance is ≈ 3000 gauss and a high resolution ($\omega\tau = \mu B \geq 5$) is realized for samples having mobilities of $170,000 \text{ cm}^2/\text{Vs}$. At $\lambda = 500 \mu$ (600 Gc/sec) the required mobility for the same resolution is only $20,000 \text{ cm}^2/\text{Vs}$.

Thus short wavelengths are very useful in a study of the cyclotron resonance of Te; samples of high mobility are pathologically sensitive to strains and successive coolings. We have found reproducible results of measurements of effective mass in Te and conclude, as did Mendum and Dexter,¹⁾ that the maximum of the valence band has the shape of an ellipsoid of revolution and have been able to exhibit an anisotropy of the relaxation time.

§ 2. Experimental Set-Up

Successively using three different carcinotrons made by C. S. F., we have performed experiments in the wavelength bands 500–600 μ , 700–

800 μ and 900–1000 μ . In Fig. 1 the power output of one of these tubes is shown as a function of carcinotron line voltage and wavelength. The maximum power output is approximately 20 mw. The high voltage power supply for the line voltage is stabilized to 2×10^{-5} . The wave is propagated through an oversized waveguide (a) in Fig. 2, generally a 4 mm guide or a circular tube. The carcinotrons are mounted on a mobile support which enables the polarization direction of the R. F. electric field to be rotated relative to sample crystal axes and magnetic field direction. Using an electromagnet external to the cryostat, fields transverse to the wave-guide (Voigt configuration) up to 28,000 gauss can be applied. Another system which utilizes a superconducting solenoid allows us longitudinal fields (Faraday configuration) up to 60,000 gauss. For transmission experiments, as shown in Fig. 2a, the power transmitted through the sample (b) is detected by bolometer (c) which is in thermal contact with the helium bath (d) and located in

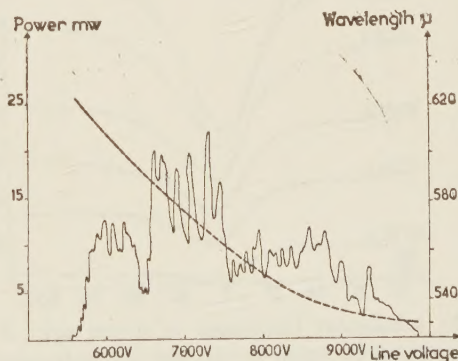


Fig. 1. Power output of carcinotron CO 05 as a function of line voltage and λ .

[†] Partly supported by the European Office of Aerospace Research (grant AFEOAR 6545).

* Ce travail recouvre partiellement le travail de these de Doctorat d'Etat es Sciences physiques devant être soutenu a la Faculté des Sciences de Paris en 1966 et enregistré au C. N. R. S. sous le numero 432.

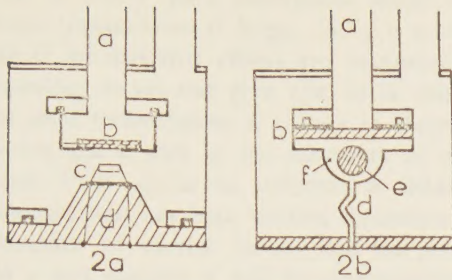


Fig. 2. The experimental arrangements.

a vacuum chamber. In another system (Fig. 2b) sample absorptivity is determined by measuring the sample temperature rise with bolometer (e) shielded (f) from microwaves and in good thermal contact with the sample. Detectors used are carbon resistors at 1.6°K and Ga doped Ge at 4.2°K.

The samples of Te used had mobilities of the order of 50,000 cm²/Vs and 2-3×10¹³ carriers cm³ at 4.2°K. Samples were small pieces approximately 2×4×1.5 mm large.

§ 3. Propagation Conditions

Since the experiments described here on Te were performed in the Voigt configuration we now consider the problem of propagation in this geometry, (Fig. 3). Magneto propagation theory²⁾ assuming classical skin effect conditions, isotropic mass and relaxation time τ , gives the following expressions for the propagation constants:

$$k_0^2 = (\omega/c)^2 \epsilon_{\parallel} \quad (\text{ordinary wave}), \quad (1)$$

for the electric field E polarized along the magnetic field B and

$$k_e^2 = (\omega/c)^2 (\epsilon_{\perp}^2 + \epsilon_{\times}^2) \epsilon_{\perp}^{-1} \equiv (\omega/c)^2 \epsilon_e, \quad (2)$$

(extraordinary wave)

for $E \perp B$, where

$$\epsilon_{\perp} = \epsilon_l + \frac{\omega_p^2}{i\omega} \left[\frac{i\omega + \tau^{-1}}{(i\omega + \tau^{-1})^2 + \omega_c^2} \right],$$

$$\epsilon_{\times} = \frac{i\omega_p^2}{\omega} \frac{\omega_c}{(i\omega + \tau^{-1})^2 + \omega_c^2},$$

$$\epsilon_{\parallel} = \epsilon_l - \frac{\omega_p^2}{\omega^2} [1 - i(\omega\tau)^{-1}]^{-1},$$

where $\omega_p^2 = 4\pi ne^2 m^{*-1}$, ω the operating frequency, ω_c the cyclotron frequency and ϵ_l the lattice dielectric constant.

In the experiments performed on Te $\omega_p < \omega$ and therefore $k_0 > 0$. Hence, the ordinary wave propagated but gave rise to no cyclotron reso-

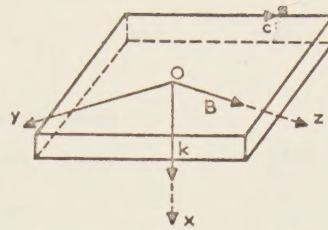



Fig. 3. Orientation of magnetic field and rf electric field in experiments.

nance as there were no tilted orbits.²⁾ For the extraordinary wave $E_z/E_y = \epsilon_{\times}/\epsilon_{\perp} \ll 1$ in the experimental conditions, hence there were no screening, longitudinal waves and resonance in k_e occurs for $\omega_e = \omega$. Since under these conditions the variation of the real part of k_e is quite small, the experiment was best carried out by measuring the total transmission. Experimental effects due to standing waves in the sample were observed. These were interpreted theoretically by calculating the power transmission coefficient for an infinite dielectric slab of thickness l ,

$$T = 4|2 \cos k_e l + i(kk_e^{-1} + k_e k^{-1}) \sin k_e l|^{-2} \dots \quad (3)$$

where k_e is given by eq. (2) and $k = \omega/c$. Equation (3) was computed by machine as a function of four parameters $\alpha = (\omega_p \tau)^2$, $\beta = \omega \tau$, $\gamma = 2\pi l/\lambda$ where λ is the free space wavelength and ϵ_l which was chosen to be 23.6 for $E \perp c$ and 39.7 for $E \parallel c$.³⁾ The results of calculation are given in Fig. 4 and correspond to $\alpha = 1.63$ with $\beta = 6$ and a thickness of 1.6 mm.

A small variation in γ approximately corresponds to a small variation of ω . The curve in Fig. 4 ($\gamma = 10.32$) which corresponds to approximately 18 half wavelengths in the sample

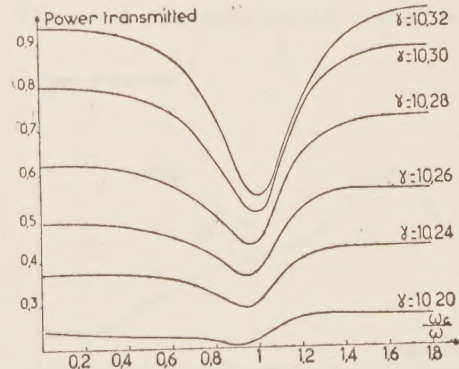Fig. 4. The results of theoretical calculation of transmission as a function of magnetic field and γ as parameter.



Digitized by the Internet Archive
in 2026

https://archive.org/details/IA41549003_0021

has a nearly pure absorption shape and the total transmission is large. As γ is varied from 10.32 the dielectric effects are magnified by the standing waves and give rise to a diminution of total transmission, a change in shape of the curve and a shift in the minimum of transmission from $\omega_c = \omega$ to different B fields. The transmission has been studied theoretically as a function of carrier density and the periodicity in γ and suggests it will be experimentally possible to measure ϵ_l and its anisotropy. The values for ϵ_l used in the calculation are those obtained at $\lambda = 6 \mu$.³⁾

§ 4. Experimental Results

The transmission experiments on Te were made for λ between 730 to 940 μ ; some results are shown in Fig. 5. Recordings A , B and C

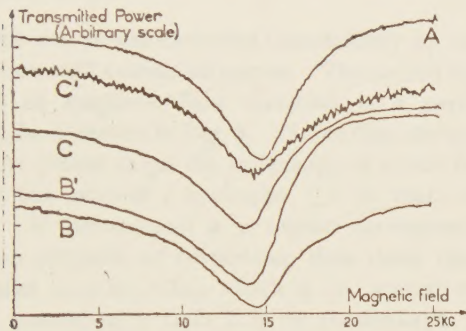


Fig. 5. Experimental transmission records for $\lambda = 930 \mu$ for various different angles of B in a parallel sample (curves A , B , C). B' and C' records are made at the same orientations as B and C but frequency was different by $\sim 0.1\%$.

were made for three different orientations of B in the plane formed by the trigonal (c) and binary axes, ($\equiv$ parallel sample). Recordings B' and C' were made for the same corresponding orientation as in B and C but with the frequency shifted by a few tenths of a percent. The minimum of C' has shifted to higher field and, that of B' to lower field while both curves are distorted from a pure absorption shape. The effective mass deduced from a distorted curve like B' was corrected by comparison with the theoretical curve corresponding to its particular shape. The estimated error in mass due to this procedure is 2%. The effective masses taken from the records for parallel samples and perpendicular samples (B always $\perp c$) are shown in Fig. 6. A single effective mass appears in the results. To within the spread of data for

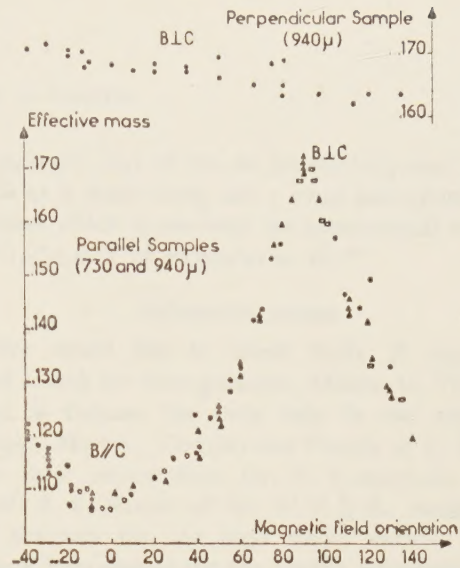


Fig. 6. Experimental cyclotron mass as a function of crystal angle deduced from experiments.

a perpendicular sample one deduces, as was found by Mendum and Dexter,¹⁾ that the valence band maximum can be represented by an ellipsoid of revolution about the c axis. Thus these ellipsoids probably occur at points M and P in the Brillouin zone according to Hulin.⁴⁾ The constants for the mass ellipsoids were found to be

$$m_1 = m_2 = 0.109m_0 \pm 0.003m_0$$

$$m_3 = 0.264m_0 \pm 0.008m_0.$$

When the magnetic field was along the binary direction, a deformation of the transmission records appeared at low B and is shown in Fig. 7. This might be interpreted as due to a warping of the ellipsoid and a further account of this will be given elsewhere.

The $\omega\tau$ of the experimental cyclotron reso-

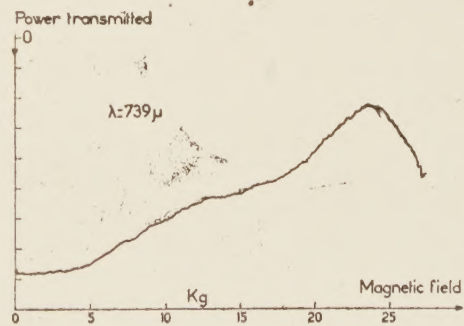


Fig. 7. A deformed resonance curve for B near the binary axis.

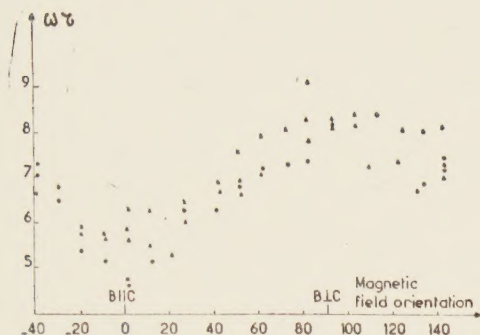


Fig. 8. $\omega\tau$ as a function of the direction of B for a parallel sample obtained from the experimental curve shapes.

nance curves was extracted theoretically by comparison with calculated curves. The $\omega\tau$ as a function of magnetic field direction in a parallel sample is shown in Fig. 8. If one uses the mean of the points to get the anisotropy in τ , one finds that the ratio of τ cyclotron $\perp c$ to that $\parallel c$ is $3/2$. If one assumes a τ tensor corresponding to an ellipsoid of revolution, then these results predict $\tau_{33} \cong 3\tau_{11} = 3\tau_{22}$ which is in accord with the theoretical τ ratio 2.29 of Dubinskaya and Farbshtein.⁶⁾ The spread in points is quite large and one should regard the result with caution. However, if one takes the ratio σ_{33}/σ_{11}

$= (\tau_{33}m_1)/(\tau_{11}m_3)$ of the dc conductivity one gets 1.24 as a result using our τ ratio and cyclotron masses which agrees with the experimental value of 1.25 ± 0.15 of Parfen'ev *et al.*⁶⁾

Acknowledgements

We would like to thank Profs. P. Aigrain and J. Bok for their guidance, Messrs. H. Thome and B. Delmas for their help in the experiments, Messrs. Convert and Yeouta of C. S. F. for their cooperation, Dr. Y. Kossitchkin and Prof. S. S. Shalyt of the U. S. S. R. Academy of Sciences for the high purity samples and Texas Instruments for the Ge-Ga bolometer assemblies.

References

- 1) J. H. Mendum and R. N. Dexter: *Bull. Amer. Phys. Soc.* **9** (1964) 632.
- 2) G. E. Smith, L. C. Hebel and S. J. Buchsbaum: *Phys. Rev.* **129** (1963) 154.
- 3) R. S. Caldwell and H. Y. Fan: *Phys. Rev.* **114** (1959) 664.
- 4) M. Hulin: *J. Phys. Chem. Solids* **27** (1966) 441.
- 5) L. S. Dubinskaya and I. I. Farbshtein: *JETP Letters* **2** (1965) 195.
- 6) R. V. Parfen'ev and A. M. Pogarskii, I. I. Farbshtein and S. S. Shalyt: *Soviet Physics-Solid State* **4** (1963) 2620.

